



SIQUAL 8519 Steel

Designation by Standards

Brand Name	Ravne	Mat. No.	DIN	EN	AISI/SAE
SIQUAL 8519	PO735	1.8519	-	31CrMoV9	-

Chemical Composition (in weight %)

C	Si	Mn	Cr	Mo	Ni	V	W	Others
0.30	max. 0.40	0.55	2.50	0.20	-	0.15	-	-

Description

Al-alloyed nitriding steel grade for large-sections.

Applications

Structural parts with high surface hardness - piston rods, extruders, cylinders, shafts, straightening tools, measuring tools, etc.

Physical properties (average values) at ambient temperature


Modulus of elasticity [$10^3 \times \text{N/mm}^2$]: 210

Density [g/cm^3]: 7.73


Coefficient of Linear Thermal Expansion $10^{-6} \text{ }^\circ\text{C}^{-1}$

-191 to +16 $^\circ\text{C}$	20-100 $^\circ\text{C}$	20-200 $^\circ\text{C}$	20-300 $^\circ\text{C}$	20-400 $^\circ\text{C}$	20-500 $^\circ\text{C}$
9.1	11.1	12.1	12.9	13.5	13.9

Continuous Cooling Transformation (CCT) Diagram

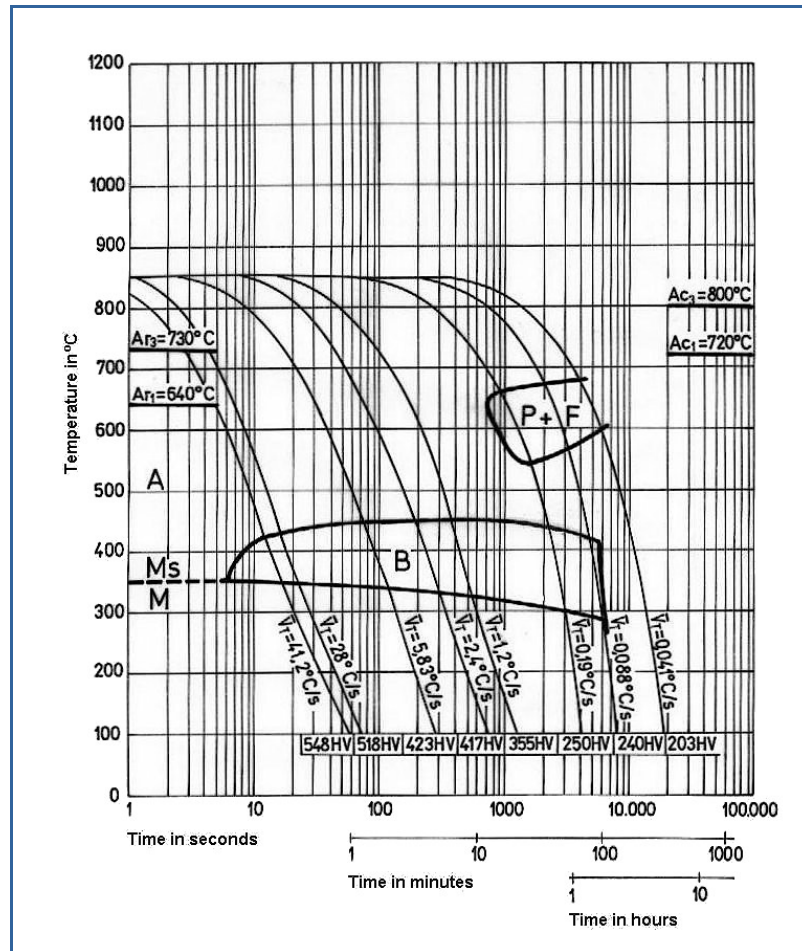

Time-Temperature Transformation (TTT) Diagram

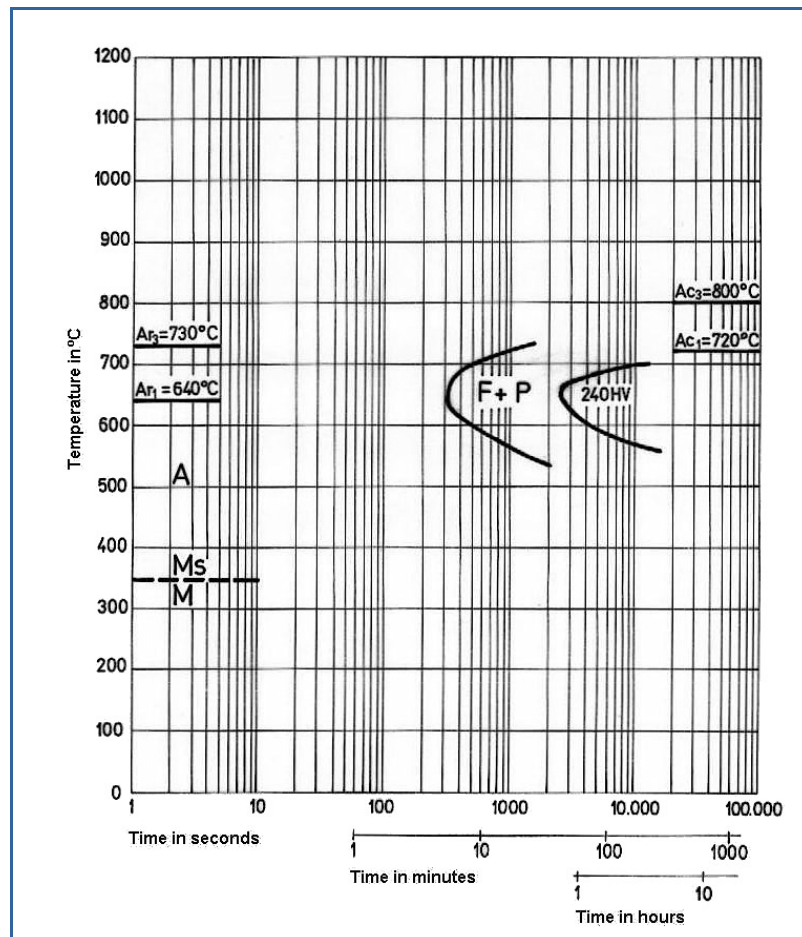

Soft Annealing

Heat to 650-720°C, cool slowly. This will produce a maximum Brinell hardness of 248.

Hardening

Harden from a temperature of 870-930°C followed by oil/polymer or water quenching.

Tempering

Tempering temperature: 580-700°C.

Nitriding


Temperature: 480-570°C.

Surface hardness after nitriding: 800 HV

Mechanical Properties in Quenched and Tempered Condition

Diameter (mm)	0.2 proof stress (N/mm ²)	Tensile strength (N/mm ²)	Elongation (%)	Reduction (%)	Notch impact energy (ISO-V) (J)
16-40	900	1100-1300	9	-	25
41-100	800	1000-1200	10	-	30
101-160	700	900-1100	11	-	35
161-250	650	850-1050	12	-	40

Mechanical Properties in Quenched and Tempered Condition

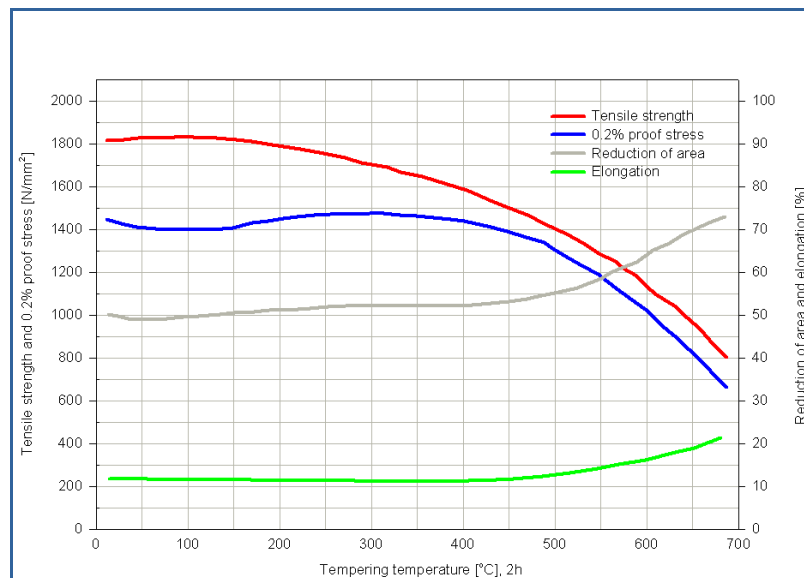

Forging

Hot forming temperature: 1050-850°C.

Machinability

No data.

Forms manufactured: Please see the [Dimensional Sales Program](#).

Disclaimer

The information and data presented herein are typical or average values and are not a guarantee of maximum or minimum values. Applications specifically suggested for material described herein are made solely for the purpose of illustration to enable the reader to make his own evaluation and are not intended as warranties, either express or implied, of fitness for these or other purposes. There is no representation that the recipient of this literature will receive updated editions as the become available.

Unless otherwise specified, registered trademarks are property of SIJ Metal Ravne company. Copyright 2016 by SIJ Metal Ravne d.o.o. All rights reserved. Contact our [Sales Office](#) for more information.